


PT. EVANINDO MEGA PERSADA

QUALITY CONTROL DAILY INSPECTION REPORT

No. Section	2 9957 0521	Description	SOLAR PANEL TYN-355 11/8x21/4" (27.72x54.72mm) [1.50]	Date	
-------------	-------------	-------------	--	------	--

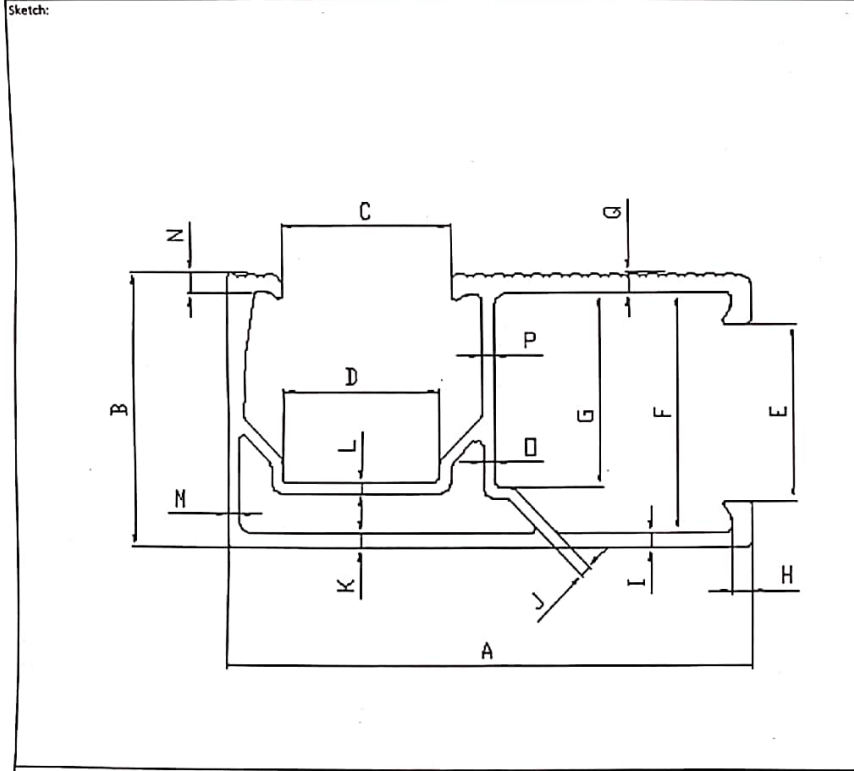

Point	Standard	Result
A	54.72 ±0.61	54.75
B	27.72 ±0.31	27.60
C	17.80 ±0.40	17.85
D	16.37 ±0.23	16.30
E	17.80 ±0.40	17.64
F	24.10 ±0.25	24.02
G	19.60 ±0.23	19.53
H	2.00 ±0.10	1.96
I	1.50 ±0.10	1.46
J	1.10 ±0.10	1.00
K	1.50 ±0.10	1.50
L	1.10 ±0.10	1.00
M	1.10 ±0.10	1.03
N	2.10 ±0.10	2.02
O	1.20 ±0.10	1.10
P	1.40 ±0.10	1.34
Q	2.10 ±0.10	2.00

Item Inspection		Times	Unit	Tech Requirement	Result	
					Test Data	Remark
Strength	Tensile Strength	n=3	Mpa	>270	292	OK
	Yield Strength		MPa	>225	260	OK
	Elongation		%	>8	11	OK
	Weber Hardness		HW	>14	15	OK
Thickness of Anodization		n=4	µm	Average Thickness >10	11.5	OK
				Partial Thickness >8	11.0	OK
Sealing of Anodizing		n=1	P	<30	11 - 15	OK

Chemical composition analysis result :

Item Inspection	Si	Mg	Cu	Fe	MN	Zn	Cr	Ti
Unit	%	%	%	%	%	%	%	%
Tech Requirements	0.6-0.9	0.4-0.6	<0,1	<0,35	<0,1	<0,1	<0,1	<0,1
Result	0.66	0.54	0.00	0.18	0.01	0.00	0.07	0.01
Conclusion	OK	OK	OK	OK	OK	OK	OK	OK

Comment	Spv. QC	QC	Ka. QC
	(.....)	(.....)	(.....) 19/5/20